

## Acetate/Di-2-pyridyl Ketone Oximate “Blend” as a Source of High-Nuclearity Nickel(II) Clusters: Dependence of the Nuclearity on the Nature of the Inorganic Anion Present

Theocharis C. Stammatos,<sup>†</sup> Eleanna Diamantopoulou,<sup>†</sup> Catherine P. Raptopoulou,<sup>‡</sup> Vassilis Psycharis,<sup>‡</sup> Albert Escuer,<sup>\*,§</sup> and Spyros P. Perlepes<sup>\*,†</sup>

Department of Chemistry, University of Patras, Patras 26504, Greece, Institute of Materials Science, NCSR “Demokritos”, Aghia Paraskevi Attikis 15310, Greece, and Departament de Química Inorgànica, Universitat de Barcelona, Diagonal 647, Barcelona 08028, Spain

Received November 28, 2006

The use of di-2-pyridyl ketone oxime [(py)<sub>2</sub>CNOH] in reactions with Ni(O<sub>2</sub>CMe)<sub>2</sub>·4H<sub>2</sub>O, in the presence or absence of extra inorganic anions (N<sub>3</sub><sup>-</sup> and SCN<sup>-</sup>) has led to Ni<sub>4</sub>, Ni<sub>5</sub>, and Ni<sub>7</sub> clusters; the magnetic study of the heptanuclear nickel(II) complex reveals an S = 3 ground state.

Synthetic access to high-nuclearity 3d metal clusters has allowed the experimental observation of exciting phenomena in the field of molecular magnetism, such as “single molecule magnetism”,<sup>1</sup> and the study of synthetic models of the active sites in metalloproteins.<sup>2</sup> However, the factors that influence the synthesis of high-nuclearity clusters are still not well understood; thus, there is a continuing need for new synthetic procedures to such species. There are two main trends in the field: the “designed synthesis”<sup>3</sup> and the “serendipitous assembly”.<sup>4</sup> The latter approach lacks control over the product, but it has proven to be extremely successful in the synthesis of clusters with interesting properties;<sup>5</sup> it uses flexible organic ligands that impose little or no geometry. One such ligand is di-2-pyridyl ketone oxime [IUPAC name: dipyridin-2-yl-methanone oxime, (py)<sub>2</sub>CNOH], whose anion is a versatile ligand for a variety of research objectives.<sup>6</sup>

We have been exploring “ligand blend” reactions involving (py)<sub>2</sub>CNO<sup>-</sup> and carboxylates as a means to high-nuclearity species. Our results with Cr,<sup>7</sup> Mn,<sup>8</sup> Fe,<sup>9</sup> Co,<sup>10</sup> and Cu<sup>11</sup> have been very encouraging. We have thus decided to extend the exploration of the general (py)<sub>2</sub>CNO<sup>-</sup>/RCO<sub>2</sub><sup>-</sup> “blend” in Ni chemistry, and we can now report that the Ni<sup>II</sup>/(py)<sub>2</sub>CNO<sup>-</sup>/MeCO<sub>2</sub><sup>-</sup> reaction system has provided access to tetra-, penta-, and heptanuclear clusters.

The reaction between Ni(O<sub>2</sub>CMe)<sub>2</sub>·4H<sub>2</sub>O and (py)<sub>2</sub>CNOH in a 1:1 molar ratio in Me<sub>2</sub>CO/H<sub>2</sub>O (5:1, v/v) gave a dark-red solution from which, upon slow evaporation at room temperature, dark-red crystals of the neutral complex [Ni<sub>5</sub>(O<sub>2</sub>CMe)<sub>7</sub>{(py)<sub>2</sub>CNO}(H<sub>2</sub>O)]·0.5Me<sub>2</sub>CO·3.2H<sub>2</sub>O (**1**·0.5Me<sub>2</sub>CO·3.2H<sub>2</sub>O) were subsequently isolated in 60% overall yield. The molecular structure<sup>12</sup> of complex **1** (Figure 1) consists of five Ni<sup>II</sup> atoms in a closed, cagelike arrangement. The

\* To whom correspondence should be addressed. E-mail: albert.escuer@qi.ub.es (A.E.), perlepes@patras.upatras.gr (S.P.P.).


<sup>†</sup> University of Patras.

<sup>‡</sup> NCSR “Demokritos”.

<sup>§</sup> Universitat de Barcelona.


- (1) For excellent reviews, see: (a) Christou, G.; Gatteschi, D.; Hendrickson, D. N.; Sessoli, R. *MRS Bull.* **2000**, 25, 66. (b) Gatteschi, D.; Sessoli, R. *Angew. Chem., Int. Ed.* **2003**, 42, 268. (c) Aromi, G.; Brechin, E. K. *Struct. Bonding (Berlin)* **2006**, 122, 1.
- (2) Ferreira, K. N.; Iverson, T. M.; Maghlaoui, K.; Barber, J.; Iwata, S. *Science* **2004**, 303, 1831.
- (3) Fujita, M. *Chem. Soc. Rev.* **1998**, 27, 417.
- (4) Winpenny, R. E. P. *J. Chem. Soc., Dalton Trans.* **2002**, 1.
- (5) (a) Bell, A.; Aromi, G.; Teat, S. J.; Wernsdorfer, W.; Winpenny, R. E. P. *Chem. Commun.* **2005**, 2808. (b) Aromi, G.; Parsons, S.; Wernsdorfer, W.; Brechin, E. K.; McInnes, E. J. L. *Chem. Commun.* **2005**, 5038. (c) Murugesu, M.; Habrych, M.; Wernsdorfer, W.; Abboud, K. A.; Christou, G. *J. Am. Chem. Soc.* **2004**, 126, 4766.

- (6) For reviews, see: (a) Chaudhuri, P. *Coord. Chem. Rev.* **2003**, 243, 143. (b) Milios, C. J.; Stammatos, Th. C.; Perlepes, S. P. *Polyhedron* **2006**, 25, 134 (Polyhedron Report).
- (7) Stammatos, Th. C.; Pringouri, K. V.; Raptopoulou, C. P.; Vicente, R.; Psycharis, V.; Escuer, A.; Perlepes, S. P. *Inorg. Chem. Commun.* **2006**, 1178.
- (8) Milios, C. J.; Kyritsis, P.; Raptopoulou, C. P.; Terzis, A.; Vicente, R.; Escuer, A.; Perlepes, S. P. *Dalton Trans.* **2005**, 501.
- (9) Stammatos, Th. C.; Boudalis, A. K.; Sanakis, Y.; Raptopoulou, C. P. *Inorg. Chem.* **2006**, 45, 7372.
- (10) Stammatos, Th. C.; Dionyssopoulou, S.; Efthymiou, G.; Kyritsis, P.; Raptopoulou, C. P.; Terzis, A.; Vicente, R.; Escuer, A.; Perlepes, S. P. *Inorg. Chem.* **2005**, 44, 3374.
- (11) Stammatos, Th. C.; Vlahopoulou, J. C.; Sanakis, Y.; Raptopoulou, C. P.; Psycharis, V.; Boudalis, A. K.; Perlepes, S. P. *Inorg. Chem. Commun.* **2006**, 9, 814.
- (12) Crystal structure data for **1**·0.5Me<sub>2</sub>CO·3.2H<sub>2</sub>O: C<sub>48.5</sub>H<sub>56.4</sub>Ni<sub>5</sub>N<sub>9</sub>O<sub>21.7</sub>, M<sub>w</sub> = 1406.10, monoclinic, space group P2<sub>1</sub>/n with a = 16.8789(15) Å, b = 25.140(2) Å, c = 18.2298(16) Å, β = 113.630(3)°, V = 7086.8(10) Å<sup>3</sup>, T = 298 K, Z = 4, R<sub>1</sub> [I > 2σ(I)] = 0.0764, wR<sub>2</sub> = 0.2058 (F<sup>2</sup>, all data). Crystal structure data for **2**·2MeOH·1.7H<sub>2</sub>O: C<sub>51.2</sub>H<sub>51.2</sub>Ni<sub>4</sub>N<sub>13</sub>O<sub>12.9</sub>S, M<sub>w</sub> = 1321.90, triclinic, space group P $\bar{1}$  with a = 16.390(13) Å, b = 15.295(11) Å, c = 14.013(10) Å, α = 73.92(2)°, β = 69.26(3)°, γ = 66.57(3)°, V = 2976(4) Å<sup>3</sup>, T = 298 K, Z = 2, R<sub>1</sub> [I > 2σ(I)] = 0.0604, wR<sub>2</sub> = 0.1752 (F<sup>2</sup>, all data). Crystal structure data for **3**·2MeCN·12.2H<sub>2</sub>O: C<sub>82</sub>H<sub>100.4</sub>Ni<sub>7</sub>N<sub>26</sub>O<sub>32.2</sub>, M<sub>w</sub> = 2376.32, monoclinic, space group P2/a with a = 21.475(9) Å, b = 21.955(9) Å, c = 11.352(5) Å, β = 96.393(12)°, V = 5319(4) Å<sup>3</sup>, T = 298 K, Z = 2, R<sub>1</sub> [I > 2σ(I)] = 0.0453, wR<sub>2</sub> = 0.1307 (F<sup>2</sup>, all data).

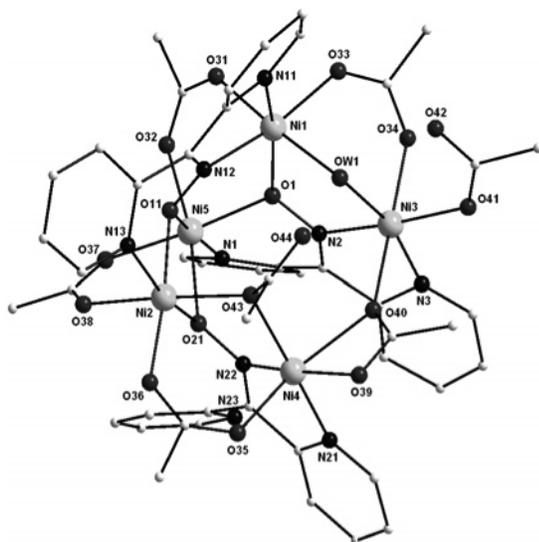


**Figure 1.** Molecular structure of complex **1** with selected atom labeling.

**Chart 1.** Crystallographically Established Coordination Modes of  $(\text{py})_2\text{CNO}^-$  in Complexes **1–3** and the Harris Notation That Describes These Modes

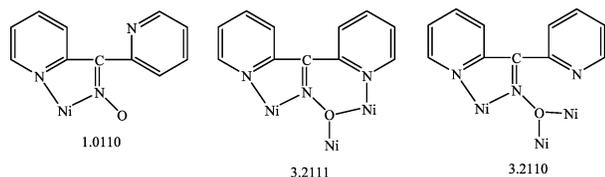


metal ions are held together through acetate, oximate, and aquo ligands. All  $\text{Ni}^{\text{II}}$  atoms are distorted octahedral. Two  $(\text{py})_2\text{CNO}^-$  ions function as 3.2111 ligands (Harris notation;<sup>13</sup> Chart 1), forming five-membered (NCCNNi) and six-membered (NCCNONi) chelating rings around two  $\text{Ni}^{\text{II}}$  atoms with the deprotonated oximate O atom bound to an extra  $\text{Ni}^{\text{II}}$  atom (Ni1 and Ni5). The third  $(\text{py})_2\text{CNO}^-$  group behaves as a 3.2110 ligand, with the deprotonated oximate O atom bridging two  $\text{Ni}^{\text{II}}$  atoms (Ni2 and Ni5), leaving the second 2-pyridyl N atom (N23) unbound. The seven  $\text{MeCO}_2^-$  groups adopt four different coordination modes. Four of them are bound through the familiar 2.11 mode (those containing O31/O32, O33/O34, O35/O36, and O37/O38), and the remaining three are arranged in the relatively rare 2.21 (O39/O40), 2.20 (O43), and 1.10 (O41) modes. Ni1 and Ni3 atoms are further bridged by an O atom (OW1) that belongs to the aquo ligand, which is hydrogen-bonded to the uncoordinated acetate O atoms O42 and O44.

The addition of  $\text{SCN}^-$  ions to the 1:1  $\text{Ni}(\text{O}_2\text{CMe})_2 \cdot 4\text{H}_2\text{O}/(\text{py})_2\text{CNOH}$  reaction mixture in MeOH gave the acetate-poor, cationic cluster  $[\text{Ni}_4(\text{O}_2\text{CMe})_2\{(\text{py})_2\text{CNO}\}_4](\text{SCN})(\text{OH}) \cdot 2.2\text{MeOH} \cdot 1.7\text{H}_2\text{O}$  ( $2 \cdot 2.2\text{MeOH} \cdot 1.7\text{H}_2\text{O}$ )<sup>12</sup> (Figure 2). The core consists of a tetrahedron of octahedral  $\text{Ni}^{\text{II}}$  atoms linked together by four 3.2111 (Chart 1)  $(\text{py})_2\text{CNO}^-$  ligands and two 2.11  $\text{MeCO}_2^-$  groups to form a distorted  $[\text{Ni}_4(\text{NO})_4]^{4+}$  “cube” comprising single (O) and double (N–O) atom edges. Peripheral ligation is provided by the eight 2-pyridyl N and the four acetate O atoms.

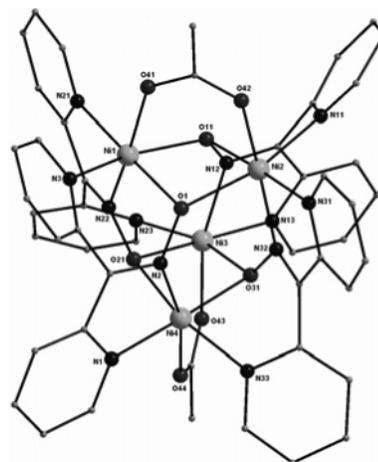

**Figure 2.** Partially labeled Pov-Ray representation of the cation of **2**.

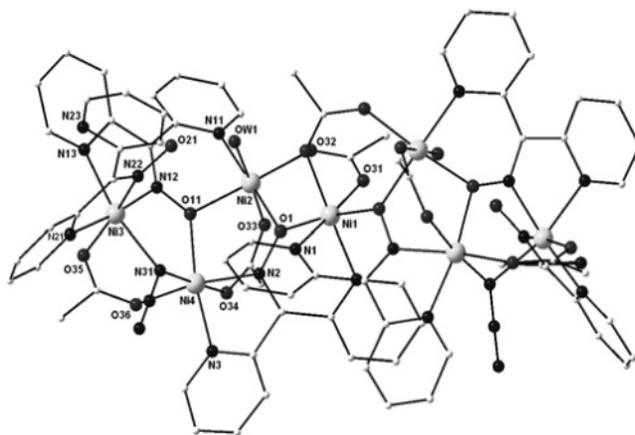

**Figure 3.** ORTEP representation of complex **3**.

Incorporation of  $\text{N}_3^-$  ions into the reaction system that led to **1**, but using  $\text{MeCN}/\text{H}_2\text{O}$  (5:1, v/v) instead of  $\text{Me}_2\text{CO}/\text{H}_2\text{O}$  (5:1, v/v) for a better quality of single crystals, gave a dark-red solution. Layering of this solution with  $\text{Et}_2\text{O}$  and slow mixing by diffusion led to the formation of dark-red crystals of  $[\text{Ni}_7(\text{N}_3)_2(\text{O}_2\text{CMe})_6\{(\text{py})_2\text{CNO}\}_6(\text{H}_2\text{O})_2] \cdot 2\text{MeCN} \cdot 12.2\text{H}_2\text{O}$  ( $3 \cdot 2\text{MeCN} \cdot 12.2\text{H}_2\text{O}$ ) in 55% yield.

The structure<sup>12</sup> consists of an unusual assembly of seven distorted octahedral  $\text{Ni}^{\text{II}}$  centers lying on crystallographic 2-fold axis, which passes through Ni1 (Figure 3). The molecule is held together by two end-on azido ligands (2.100), four 3.2111  $(\text{py})_2\text{CNO}^-$  ions, and six 2.11  $\text{MeCO}_2^-$  groups. Peripheral ligation is provided by two 1.0110  $(\text{py})_2\text{CNO}^-$  ligands (Chart 1), which bind as bidentate chelates to Ni3 (and to its symmetry-related partner), and two terminal aquo ligands, which complete the coordination sphere of Ni2 (and its symmetry-related metal ion). Without considering the bridging acetates as part of the core, the latter appears to be  $[\text{Ni}_7(\eta^1\text{-}\mu\text{-N}_3)_2(\mu_3\text{-ON})_4]^{8+}$ . The molecule can be conveniently described as consisting of two  $[\text{Ni}_3(\mu\text{-N}_3)(\mu\text{-O}_2\text{CMe})_2(\eta^1\text{-O}_2\text{CMe})\{\mu_3\text{-}(\text{py})_2\text{CNO}\}\{\mu\text{-}(\text{py})_2\text{CNO}\}\{\eta^2\text{-}(\text{py})_2\text{CNO}\}]^-$  subunits, each linked to the central Ni1 ion through one acetate O atom (O31 and O31'), one oximate O atom (O1 and O1'), and one 2-pyridyl N atom (N1' and N1); as a result of this connection, the terminal acetates of the hypothetical subunits become bidentate bridging, while the

(13) Coxall, R. A.; Harris, S. G.; Henderson, D. K.; Parsons, S.; Tasker, P. A.; Winpenny, R. E. P. *J. Chem. Soc., Dalton Trans.* **2000**, 2349.

## COMMUNICATION


oximate O atoms (O1 and O1') become bridging and the uncoordinated 2-pyridyl N atoms (N1' and N1) bind to Ni1, giving an overall  $\mu_3$  character in the corresponding  $(\text{py})_2\text{CNO}^-$  ligands. Complex **3** joins a small family of structurally characterized heptanuclear nickel(II) clusters with O and/or N ligation.<sup>14</sup>

The  $\chi_{\text{M}}T$  value for **1** is  $4.34 \text{ cm}^3 \text{ K mol}^{-1}$  at room temperature. As the temperature is lowered,  $\chi_{\text{M}}T$  experiences a gradual decrease, reaching a value of  $0.63 \text{ cm}^3 \text{ K mol}^{-1}$  at 2 K. A reliable fit of the experimental data is not possible because of the overparametrization imposed by the asymmetry of this compound. In addition, it may have several triangular interactions that can give rise to competitive or frustrated interactions, giving a complicated set of superexchange pathways. A qualitative analysis of the  $\chi_{\text{M}}T$  vs  $T$  plot indicates an overall antiferromagnetic interaction. The shape of the curve and the  $\chi_{\text{M}}T$  value at low temperatures suggest a ground state close to a frustration point between the  $S = 0$  spin level and at least one of the  $S = 1$  spin levels. This fact is corroborated by the magnetization measurement performed at 2 K, which tends to a value close to only one electron under a field of 5 T. Trials to fit the experimental data with an oversimplified  $3J$  model give multiple mathematical minima and poorly reasonable  $J$  values despite the good simulation of the experimental data (see the Supporting Information).

The value of the  $\chi_{\text{M}}T$  product for **2** decreases gradually upon cooling ( $4.07 \text{ cm}^3 \text{ K mol}^{-1}$  at 300 K) until ca. 100 K, and below this temperature, it decreases quickly down to a value of  $0.13 \text{ cm}^3 \text{ K mol}^{-1}$  at 4 K. This behavior is consistent with dominant antiferromagnetic interactions and an  $S = 0$  ground state; the latter is corroborated by the appearance of a maximum in  $\chi_{\text{M}}$  at 18 K.

Inspection of the molecular structure reveals that there are only two exchange parameters between the metal centers. The first one ( $J_1$ ) is associated with the  $\text{Ni1}\cdots\text{Ni2}$  and  $\text{Ni3}\cdots\text{Ni4}$  interactions through two oximate  $\mu\text{-O}$  atoms and one carboxylate bridge and the second one ( $J_2$ ) with the  $\text{Ni1}\cdots\text{Ni3}$ ,  $\text{Ni1}\cdots\text{Ni4}$ ,  $\text{Ni2}\cdots\text{Ni3}$ , and  $\text{Ni2}\cdots\text{Ni4}$  interactions, each involving two diatomic oximate groups. Best-fit<sup>15</sup> parameters employing the spin Hamiltonian  $H = -J_1(S_1S_2 + S_3S_4) - J_2(S_1S_3 + S_1S_4 + S_2S_3 + S_2S_4)$  are  $J_1 = -2.7 \text{ cm}^{-1}$ ,  $J_2 = -12.1 \text{ cm}^{-1}$ , and  $g = 2.11$ . The weak antiferromagnetic interaction  $J_1$  agrees with the expected value for  $\text{Ni-O-Ni}$  bond angles around  $94^\circ$ , whereas  $J_2$  is a normal value for  $\text{Ni-oximate-Ni}$  bridges.<sup>6,16</sup>

The  $\chi_{\text{M}}T$  product for **3** decreases gradually from a value of  $8.19 \text{ cm}^3 \text{ K mol}^{-1}$  at 300 K until a minimum of  $5.50 \text{ cm}^3 \text{ K mol}^{-1}$  at 40 K. Below this temperature, the  $\chi_{\text{M}}T$  product increases slightly and finally decreases because of zero-field-

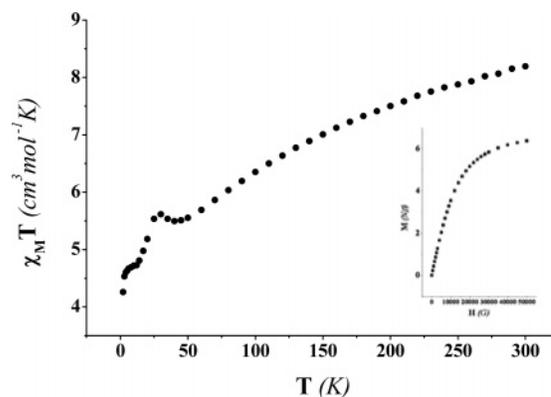

**Figure 4.** Plot of  $\chi_{\text{M}}T$  vs  $T$  for **3**. The inset illustrates the reduced magnetization vs field plot, which tends to a value close to six unpaired electrons under a field of 5 T at 2 K.

splitting and/or intermolecular interactions. The shape of the curve and the  $\chi_{\text{M}}T$  values indicate an overall antiferromagnetic or ferrimagnetic behavior with a ground state greater than  $S = 0$  (Figure 4). Magnetization measurements clearly indicate an  $S = 3$  ground state (Figure 4, inset). Compound **3** exhibits five kinds of interactions; four of them are clearly different in nature involving the azido bridge ( $J_1$ ), one diatomic oximate bridge ( $J_2$ ), the double diatomic oximate/ $\mu\text{-O}$  bridge ( $\text{Ni-O-Ni} = 110.2^\circ$ ;  $J_3$ ), and the double  $\mu\text{-O}$ /carboxylate bridge ( $\text{Ni-O-Ni} = 125.3^\circ$ ;  $J_4$ ). We refrain from presenting here the very good (and magnetically reliable) fit of the data employing the appropriate  $4J$  spin Hamiltonian because this leads to overparameterization; our efforts appear in the Supporting Information. Trials to simplify the fit with a  $3J$  model, assuming  $J_2 = J_3$ , did not give good fits.

In summary, the use of the  $(\text{py})_2\text{CNO}^-/\text{MeCO}_2^-$  “blend” has provided three new Ni clusters with interesting structures. The nuclearity of the cluster,  $[\text{Ni}_4]$  to  $[\text{Ni}_7]$ , is controlled partly by the presence or absence of an extra inorganic anion and by the identity of this anion. The combination of  $(\text{py})_2\text{CNOH}$ , carboxylate, and azide ligands with a host of other 3d transition elements or combinations of 3d with 4d, 5d, and 4f metals promises to deliver many new and exciting clusters.

**Acknowledgment.** Financial support from the European Social Fund (Operational Program for Educational and Vocational Training II, Program PYTHAGORAS I, Grant b 365.037) and the Ministerio de Educación y Ciencia of Spain (Project CTQ2006-01759) is gratefully acknowledged.

**Supporting Information Available:** Full synthetic procedures and elemental analyses of complexes **1–3**, the cores and the coupling schemes of **1–3**,  $\chi_{\text{M}}T$  vs  $T$  and  $M$  vs  $H$  for complex **1**,  $\chi_{\text{M}}T$  vs  $T$  and  $\chi_{\text{M}}$  vs  $T$  plots for complex **2**, fit details for the three clusters (in a textual form), and crystallographic data for **1**· $0.5\text{Me}_2\text{CO}$ · $3.2\text{H}_2\text{O}$ , **2**· $2.2\text{MeOH}$ · $1.7\text{H}_2\text{O}$ , **3**· $2\text{MeCN}$ · $12.2\text{H}_2\text{O}$  (CCDC Nos. 622481, 622480, and 622482, respectively) in CIF format. This material is available free of charge via the Internet at <http://pubs.acs.org>.

IC062262T

(14) For example, see: Diamantopoulou, E.; Raptopoulou, C. P.; Terzis, A.; Tangoulis, V.; Perlepes, S. P. *Polyhedron* **2002**, *21*, 2117 and references cited therein.

(15) Program CLUMAG: Gatteschi, D.; Pardi, L. *Gazz. Chim. Ital.* **1993**, *123*, 231.

(16) Weyhermüller, T.; Wagner, R.; Khanra, S.; Chaudhuri, P. *Dalton Trans.* **2000**, 2539.